



Texdecor SAS
2 Rue d'Hem
FR-59780 Willems

Your notice of
 12-07-2023

Your reference

Date
 11-03-2024


Analysis Report 23.03882.04

Modification

Required tests :

EN 13773 (2003)

Sample id	Updated information given by the client	Date of receipt
T2316438	Sohalia FR	12-07-2023




Gina Créelle
 Order responsible

This report may be reproduced, as long as it is presented in its entire form, without written permission of Centexbel.
 The results of the analysis cover the received samples. Centexbel is not responsible for the representativeness of the samples.
 In assessing compliance with the specifications, we did not take into account the uncertainty on the test results.



Samples

T2316438
Sohalia FR

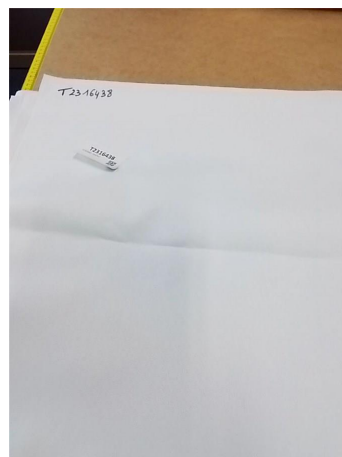



Reference: T2316438 - Sohalia FR

Textiles – Burning behaviour – Curtains and drapes - Textile fabrics - Determination of the ignitability of vertically oriented specimens.

Date of ending the test 10-08-2023
Standard used EN 1101 (1995) + A1 (2005)
Product standard EN 13773 (2003)

Deviation from the standard -

Conditioning 20°C, relative humidity 65%
Testing atmosphere 24°C, relative humidity 46%


Ignition Bottom edge

The test specimens have not been cleaned nor submitted to an accelerated ageing procedure.

Length

Flame application time (s)	Cases of ignition	Cases of non-ignition
1	0	1
2	0	1
3	0	1
4	0	1
5	0	1
10	0	1
15	0	1
20	0	5

The mean of the recorded times at which ignition was observed is calculated
No ignition within 20 s



Width

Flame application time (s)	Cases of ignition	Cases of non-ignition
1	0	1
2	0	1
3	0	1
4	0	1
5	0	1
10	0	1
15	0	1
20	0	5

The mean of the recorded times at which ignition was observed is calculated
 No ignition within 20 s

Reference: T2316438 - Sohalia FR

Textiles and textile products – Burning behaviour – Curtains and drapes. Measurement of flame spread of vertically oriented specimens with large ignition source.

Date of ending the test 11-08-2023
Standard used EN 13772 (2011)
Product standard EN 13773 (2003)

Deviation from the standard -

Conditioning 20°C, relative humidity 65%

The test specimens have not been cleaned nor submitted to an accelerated ageing procedure.

Length

	Face A	Face B	Face B	Face B
Severance 1 st thread	no	no	no	no
Severance 2 nd thread	no	no	no	no
Severance 3 rd thread	no	no	no	no
Time to sever 3 rd thread (s)	/	/	/	/
Destroyed length (mm)	120	125	130	135
Flaming debris	no	no	no	no

Width

	Face A	Face B	Face A	Face A
Severance 1 st thread	no	no	no	no
Severance 2 nd thread	no	no	no	no
Severance 3 rd thread	no	no	no	no
Time to sever 3 rd thread (s)	/	/	/	/
Destroyed length (mm)	135	135	120	135
Flaming debris	no	no	no	no

Classification in accordance with EN 13773 Class 1